

## STOCKHOLM JUNIOR WATER PRIZE

Edição 2022 – Etapa Brasil

# SustainPads: Sustainable and affordable sanitary pads from industrial by-products

**Authors:** Camilly Pereira dos Santos and Laura Nedel Drebes.

**Advisor:** Flávia Santos Twardowski Pinto.

**School:** Instituto Federal de Educação, Ciência e Tecnologia do Rio Grande do Sul (IFRS) - Campus Osório, Osório/ RS

Stockholm Junior Water  
Prize Brazil



## ACKNOWLEDGMENTS

To our Institution, *IFRS – Osório* campus for providing us with space for this research to be carried out. For providing a quality public education.

To *CNPq* (National Council for Scientific and Technological Development) for the Scientific Initiation grants and for promoting Science so that increasingly more young people can have the opportunity to make a difference in their community.

To the Cacao Show, Vidora and Hortaria Delivery industries that have provided us with the waste and given us the support to make the research possible.

We thank Professor Sérgio Migowski for his teachings and all his enthusiasm in helping us. Even physically distant, he contributed a lot for the project's growth.

## ABSTRACT

Basic sanitation is a human right guaranteed by the Federal Constitution. However, in practice, access to these basic rights is worsened, especially for 500 million women around the world who do not even have tampons and sanitary pads during their menstrual period. This is Period Poverty. In addition to the lack of access to basic hygiene materials that impacts the social sphere, synthetic tampons and sanitary pads have a negative impact on the planet, since most of their material comes from non-renewable sources, requiring tons of liters of water to manufacture. Therefore, this research developed an affordable and ecological alternative to sanitary pads considering the sustainability tripod. First, the replacement of conventional cotton was done using the complete Factorial Design  $2^2$  with response surface methodology, where the variables alkali concentration and time were evaluated in the optimization of the production of absorbent materials, testing the banana pseudo-stem fibers (BPSF) and *Açaí de juçara (AJ)* - (*Euterpe edulis* Mart). Afterwards, to replace plastic, biofilms were developed with residues from the nutraceutical industry (RNI). Finally, the prototype was created with fabric scraps using the Upcycling concept. BPSF and *AJ* showed absorptive capacities of 1274% and 1304%, respectively. The biofilms obtained with RNI showed an absorptive capacity of 87.3%. The final prototype was able to absorb 645%, while the conventional ones, 532%. Thus, the project proved to be a promising alternative to meet an urgent demand, demonstrating social, environmental, economic, and scientific relevance, meeting five of the 17 UN SDGs.

**Key words:** Pad. Accessibility. Period poverty. Industrial waste. Sustainability.

## **TABLE OF CONTENTS**

<b>1. INTRODUCTION</b>	<b>4</b>
<b>2. METHODOLOGY OR MATERIALS AND METHODS</b>	<b>6</b>
2.1 DEVELOPMENT OF ABSORBENT LAYERS	6
2.2 PREPARATION OF BIOFILMS	7
2.3 CHARACTERIZATION OF MATERIALS	7
<b>3. RESULTS</b>	<b>9</b>
3.1 DEVELOPMENT OF ABSORBENT MATERIALS	9
3.2 PREPARATION OF BIOFILMS	10
3.3 ABSORBENT PROTOTYPE	11
<b>4. CONCLUSIONS AND/OR RECOMMENDATIONS</b>	<b>12</b>
<b>5. REFERENCES</b>	<b>14</b>
ANNEX A. QUESTIONS ABOUT THE PROJECT	17

## 1. INTRODUCTION

Menstruation is a natural process of women's bodies, which requires hygienic practices so that they can continue with their regular activities during their period. Therefore, the United Nations (UN, 2014) recognized period hygiene as a public health and human rights issue. However, the alarming problems related to the lack of availability of basic period hygiene materials for a large portion of the population are increasingly present. This situation is called Period Poverty and is aggravated by the high price of sanitary pads, which end up being considered a privilege (BOROWSKI, 2011). This problem causes impacts that extend to several areas of these women's lives, such as their physical and emotional health, education, and security (GOLI, 2020).

However, the use of tampons and sanitary pads has also negatively influenced environmental issues. On average, women discard 10,000 sanitary pads during their lifetime. These are made from materials from non-renewable sources - such as plastic components from petroleum - in addition to the presence of chemical additives, taking 100 to 500 years to decompose (STEWART et al., 2009).

Regarding plastic (also used in tampons and sanitary pads), the problem is even more complex: its versatile application in the last 65 years, period in which there has been an increase in its production and has outgrown any other material produced until then (GEYER, 2017). In the disposal stage, they need to have a destination that, in most cases, is not the most appropriate. Society's high demand makes this problem get worse year after year. Experts have found that the number of single-use plastics is discarded at a speed that nature cannot absorb (VASCONCELOS, 2019). Despite the various applications and advantages, such as resistance and durability to degradation, when in constant contact with the sun and/or over the years, for example, plastic disintegrates into microparticles and these, which have a microscopic size, can cause numerous health problems (even though their absolute effects are not yet known) for Human Beings, soil pollution and, mainly, risks to Marine Life (GEYER, 2017). According to Vasconcelos (2019), there is great concern among experts regarding the impact of plastic on the oceans. About 8 million tons a year of this polymer reach the seas in the form of garbage.

In addition, tampons and sanitary pads end up demanding tons of liters of water to manufacture, since its raw material comes from cellulose, which is among the most water-consuming industrial processes. It is estimated that for every kilogram of cotton produced, 10,000 liters of water are used (GLOBO RURAL, 2021). That is, for each

absorbent, 120 liters of water are spent only on cotton production.

Although there are currently more sustainable alternatives to tampons and sanitary pads, such as menstrual cups and reusable sanitary pads, they are not accessible to a large part of the population because they require greater investment when purchased (BUSSEY, 2015). Therefore, environment-friendly menstruation is still a luxury for thousands of women who quit doing their daily activities during their period due to the fact they do not have the minimum conditions to deal with this situation.

Considering these issues that are related to the sustainability tripod (environmental, economic, and social aspects), the justification of this research highlights the need and the importance of developing a product that is affordable and at the same time environmentally safe for consumers. To provide this alternative, the use of industrial waste is a promising option, given the worrying scenario of the growth of waste generation during industrial processing, which has been a threat to nature, since these are rarely explored in terms of their possible applications. (SARAIVA et al., 2018). In this way, studying an alternative that, in addition to being ecological, is also accessible to women in situations of vulnerability, plays a fundamental role in helping the fight against menstrual poverty and in the struggle for a more sustainable society.

The study carried out in this project was based on the following problem: Is it possible to develop a sustainable alternative to tampons and sanitary pads that is accessible to lower-income people? The general objective of this research project was to develop an ecological and low-cost alternative to current sanitary pads through industrial waste. To achieve the general objective of this project, it was necessary to follow the following specific objectives: i) developing absorbent materials with fibers extracted from agro-industrial residues; ii) producing biofilms; iii) analyzing the properties of biofilms and absorbent materials; iv) evaluating the performance of the prototype developed.

## 2. METHODOLOGY OR MATERIALS AND METHODS

The methodology of this project covered applied research. The residues of banana pseudo-stem fibers (BPSF), rice husks (RH), corn cobs (CC) and *Açaí de Juçara* (AJ) were collected in agro-industries of the North Coast of Rio Grande do Sul. Waste from the Nutraceutical Industry (RNI) was supplied by Vidora Farmacêutica Ltda. Cocoa fruit residues (CFR) were supplied by Cacau Show.

### 2.1 Development of absorbent layers

The first step was the extraction of fibers from BPSF and AJ residues. The CC and RH residues were submitted to alkaline treatment according to Kenawy et al. (2021): (i) drying in an oven (80°C/24 h); (ii) immersion of the residues in an alkaline solution of NaOH 8%, 24 h; (iii) washing the residues to neutral pH; (iv) drying in an oven (80°C, 24h). BPSF and AJ were submitted to alkaline treatment according to Abdela (2020): (i) drying of residues in an oven (80°C; 24 h); (ii) immersion of these in an alkaline solution of NaOH varying the concentrations (Table 1); (iii) autoclaving varying the time (Table 1); (iv) washing the residues to neutral pH (Figure 1); (v) drying in an oven (80°C; 24h).

IMAGE 1: WASHING THE RESIDUES



Source: Authors, 2021

A  $2^2$  full factorial central composite design was used to evaluate the statistical significance of alkali concentration and treatment time on alkaline treatment for BPSF and AJ. (NETO, SCARMINIO AND BRUNS; 2001). The evaluated response factor (Y) was water uptake. Table 1 presents the coded and actual values of the experimental design. The software used to verify the model was Statistica 10.0 from Statsoft for Windows. Analysis of Variance (ANOVA) was used to assess the significance of the proposed model at 95% of reliability. The experiments were carried out in triplicate.

TABLE 1 - FACTORIAL PLANNING

Assay	Coded levels		Real levels	
	$x_1^*$	$x_2^*$	$x_1^*$	$x_2^*$
1	-1	-1	15	10
2	1	-1	45	10
3	-1	1	15	24
4	1	1	45	24
5	0	0	30	17
6	0	0	30	17
7	0	0	30	17
8	-1,41	0	5	17
9	0	-1,41	30	7

10	1,41	0	50	17
11	0	1,41	30	27

$x_1^*$  = time of treatment [min];  $x_2^*$  = Alkali concentration, NaOH [%]

Source: AUTHORS (2021).

One-way ANOVA was used to assess absorptive capacities. The Tukey test was used to identify which residue showed a significant difference in absorption capacity (MONTGOMERY, 2008).

## 2.2 Preparation of biofilms

The CFRs were initially ground to form cocoa mesocarp flour (CMF). The casting technique was used to produce the biofilms. The solutes (residues) were dissolved in the solvent (water) and the solution heated to 85°C, at 150 rpm on a magnetic stirrer, spawning a polymeric matrix that forms the film, in bain-marie (MALI; GROSSMANN; YAMASHITA, 2010). After the solution was poured into Petri dishes and oven dried at 35°C (Table 2).

TABLE 2: PRELIMINARY TESTS

Inputs	Concentrations [%]		
	CMF unsifted	CMF sifted	NIR
Assay 1	4	-	26
Assay 2	-	4	26
Assay 3	-	2	27,5
Assay 4	-	8	-
Assay 5	-	-	13
Assay 6	-	-	23
Assay 7	-	-	26

CMF = cocoa mesocarp flour; NIR = residue from the nutraceutical industry

Source: AUTHORS (2021)

## 2.3 Characterization of materials

The absorbent materials were tested for their absorption capacity with the *in natura* and treated fibers. 1g of the material was immersed in 200mL of water for 20s. Afterwards, the material was weighed, and the percentage of absorption was calculated according to IS 5405:1980 for sanitary pads and diapers (PMSN, 2020).

Biofilms were analyzed in triplicate to know their characteristics:

- 1) **Thickness**: a digital micrometer (Mitutoyo Corp. Tokyo, Japan; Model MDC-25) was used with a precision of 0.001 mm and a resolution of 0 to 25 mm.
- 2) **Humidity**: it was determined by gravimetric method (AOAC, 2005).
- 3) **Biodegradability**: the biofilms were buried in the soil for 16 days and exposed to the microorganisms present in it. Every 2 days, 20mL of water was added to maintain moisture (STOLL, 2015).
- 4) **Water absorption capacity (Swelling)**: the samples were weighed and immersed in water where they remained for 2 min. Afterwards, the film strips were placed on filter paper, to remove excess water, and weighed. The weight difference percentage was calculated (IAHNKE, 2015).

5) Mechanical Properties: From the thickness data of each strip, the mechanical properties of tensile strength [MPa], elongation at break [%] and Young's modulus [MPa] were determined using a Texture Analyser (TA.XT2i and Stable Micro Systems, UK), according to the American Society for Testing and Materials standard D882-12 (ASTM, 2012).

### 3. RESULTS

#### 3.1 Development of absorbent materials

To extract the fibers from the BPSF, the material was cut into strips and pressed using the weight of the wheels of a car. The *AJ* fibers were manually extracted (QUIRINO, 2017) (Image 2). CC and RH did not have to go through such a process. The results of the absorption tests can be seen in Table 3.

IMAGE 2 - PROCESS OF EXTRACTION OF VEGETABLE FIBERS



[SEQUENCE 1] – BPSF fiber extraction;  
[SEQUENCE 2] – *AJ* fiber extraction de.  
Source: AUTHORS (2021)

TABLE 3: RESULTS OF ABSORPTION TESTS

Fiber tests	Absorption (%)
Pseudo-stem Fiber ( <i>in natura</i> )	826,85
Pseudo-stem Fiber (treated)	1349,10
<i>Juçara</i> Fiber ( <i>in natura</i> )	695,76
<i>Juçara</i> Fiber (treated)	1327,88
Rice husk ( <i>in natura</i> )	364,11
Rice husk (treated)	535,09
Corn cob ( <i>in natura</i> )	261,27
Corn cob (treated)	256,00

Source: AUTHORS (2021)

The CC and RH did not show promising absorption capacities, being below 500% and therefore were discarded from the other processes. This fact can be attributed to the hydrophobic compounds present in greater quantities in these materials when compared to the others (FERREIRA, MACHADO, ADEMAR, 2020; FILHO, 2021).

The 2<sup>2</sup> Factorial Design with Response Surface methodology and the one-way ANOVA showed promising results (Table 4). The superscript letters demonstrate the trials that statistically presented similar (same letter) and different behaviors. In Image 3, it is possible to observe the difference between the BPSF and *AJ* fibers. Its softness, after chemical treatment, is like commercially sold cotton.

TABLE 4: RESULTS OF ABSORPTION ANALYSIS

Assay	Absorption [%]	
	$y_1^*$	$y_2^*$
1	1038,46 ± 78,45 <sup>a</sup>	1113,28 ± 31,15 <sup>a</sup>
2	1076,26 ± 68,23 <sup>a</sup>	1316,00 ± 66,29 <sup>b</sup>
3	1141,33 ± 80,95 <sup>a</sup>	1223,23 ± 117,06 <sup>a</sup>
4	1162,67 ± 43,37 <sup>b</sup>	1377,59 ± 32,74 <sup>b</sup>
5	1285,38 ± 75,50 <sup>b</sup>	1293,85 ± 70,86 <sup>b</sup>
6	1193,33 ± 63,86 <sup>b</sup>	1310,67 ± 23,63 <sup>b</sup>
7	1252,87 ± 66,39 <sup>b</sup>	1299,49 ± 74,52 <sup>b</sup>
8	1274,00 ± 2,00 <sup>b</sup>	1224,00 ± 52,65 <sup>a</sup>
9	1011,38 ± 51,48 <sup>a</sup>	1304,00 ± 42,83 <sup>b</sup>
10	1072,97 ± 39,79 <sup>a</sup>	1176,92 ± 58,16 <sup>a</sup>
11	1133,33 ± 31,72 <sup>a</sup>	1155,13 ± 25,38 <sup>a</sup>

$y_1^*$  = absorption of pseudo-stem fibers [%];  $y_2^*$  = absorption of *juçara* fibers [%].

Source: AUTHORS (2021)

IMAGE 3 – FIBERS FROM PSEUDO-STEM AND AÇAÍ BEFORE AND AFTER ALKALINE TREATMENT



[A] – *in natura* pseudo-stem fiber; [B] – treated pseudo-stem fiber (40% NaOH, 40min autoclaving).

[C] – *in natura* açai fiber; [D] – treated *juçara açai* fiber (40% NaOH, 40min autoclaving)

Source: AUTHORS (2021)

Equation 1 for the BPSF residue shows that when the treatment time is reduced and a lower concentration is used, a material with greater absorption is obtained. These results are in line with ANOVA, which showed that test number 8 (time of 5 min. and concentration of 17%) is more economical because it requires less production time.

$$Y = 1243,9 - 28,1x_1 - 39,8x_1^2 + 45,3x_2 - 90,7x_2^2 \quad \text{Equation 1}$$

When it comes to *AJ* fibers (where the interaction between the parameters was also significant), using smaller amounts of alkali and process times between 17 and 30 minutes, the best uptaking capacities were obtained. Equation 2 describes this behavior. This is also in line with the one-way ANOVA, showing that Assay 9 is the most suitable (30 min time and 7% concentration).

$$Y = 1301,1 - 36,44x_1 - 39,83x_1^2 + 4,81x_2 - 25,2x_2^2 \quad \text{Equação 2}$$

### 3.2 Preparation of biofilms

The production of biofilms was performed according to Table 2. Table 5 shows the properties of the biofilms developed, and in test 4 there was no formation of biofilms.

TABLE 5: PROPERTIES OF BIOFILMS

Assay	Average thickness [mm]	Humidity (%)	Average absorption (%)	Traction resistance (Mpa)	Elongation at break (%)	MY [Mpa]
Assay 1	0,711 ± 0,148	29,99 ± 0,24	49,86 ± 2,19	0,8 ± 0,05	30,71 ± 1,14	8,24 ± 0,8
Assay 2	0,651 ± 0,136	12,74 ± 0,23	47,05 ± 5,53	x	x	x
Assay 3	0,758 ± 0,110	13,81 ± 0,88	52,82 ± 13,91	x	x	x
Assay 5	0,300 ± 0,079	14,59 ± 0,69	87,3 ± 15,21	x	x	x
Assay 6	0,514 ± 0,174	13,54 ± 0,16	45,29 ± 8,38	0,86 ± 0,09	106,9 ± 7,93	3,23 ± 0,36
Assay 7	0,560 ± 0,133	13,31 ± 0,23	43,52 ± 6,22	1,82 ± 0,36	232,48 ± 19,56	2,82 ± 0,35

x = films that didn't make it through assay  
Source: AUTHORS (2021)

Biofilms using CMF showed intermediate absorptive capacities. In addition, the biofilms proved to be fragile and non-homogeneous. Thus, the best results were obtained using the nutraceutical residues (Image 4).

IMAGE 4: ASSAY 7 BIOFILM



Source: Authors, 2021

The average thickness of all films obtained in the tests was less than 1 mm, all in accordance with the D882 standard (ASTM, 2012). The results obtained in the moisture tests showed an average of 16.33%, being like those found by Silva (2011), providing adequate properties to the final product. Considering the application of biofilms, the best result for the lower layer was the one obtained in Test 7 (43.52%), as it had greater impermeability. On the other hand, the upper biofilm layer requires that the absorptive capacity be greater so that when the fluid meets the biofilm, it is absorbed instantly. Thus, the best result was obtained in Trial 5 (87.3%).

The biodegradability results were promising, with an average of 49.92%, especially when compared to conventional plastics used in commercialized tampons and sanitary pads, which take 100 to 500 years to decompose (STEWART et al., 2009).

Regarding the mechanical properties, the best results of tensile strength [ $1.82 + 0.36$  (Mpa)], elongation at break [ $232.48 + 19.56$  (%)], Young's modulus [ $2.82 + 0.35$  (Mpa)] were obtained with Assay 7. This is the most promising biofilm, as it has the smallest Young's modulus, therefore being the least rigid; and the best tensile strength and elongation results, demonstrating the flexibility and elasticity necessary for the prototype.

### 3.3 Absorbent prototype


Using fabric scraps made available by seamstresses in the region, the tissue casing to wrap the absorbent refill was developed (Image 5). 13 different types of fabrics were tested, with Viscolycra having the best and fastest absorption. Inside this casing is the absorbent refill (Image 6), composed of the union of plant fibers with biofilms. The final prototype can be seen in Image 7 and 8.

IMAGE 5 – CONFECTION OF THE CASING




Source: AUTHORS (2021)

IMAGE 6 – ABSORBENT REFILLS

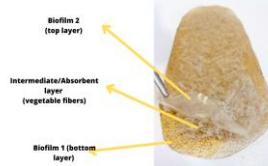


Source: AUTHORS (2021)

IMAGE 7 – REFILL + CASING

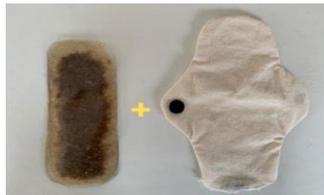

Source: AUTHORS (2021)

IMAGE 8 – PROTOTYPE OF SANITARY PAD AND ITS LAYERS:

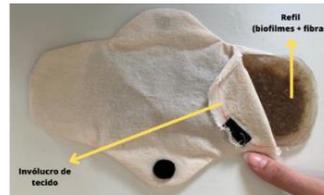

Source: AUTHORS (2021)

In this way, the concept of Upcycling was used, which consists of using raw materials for transformation into new materials in a sustainable way (VIANA, 2021). The reuse of materials is essential, given the economic aspect. The “up” means up, that is, there is an improvement of the product, and the “cycling” refers to the cyclical use of materials. This initiative contributes to the Circular Economy being more present in society and production chains.

The sanitary pad production cost was calculated using the absorption costing method, based on the central point of the factorial planning of both fibers (17% of alkali concentration and 30min of time in the autoclave), while the selling price was calculated using of the Markup method (MENDES, 2009) with a 4.5% increase in taxes and a 20% profit margin. The sale price established was R\$ 0.02.

#### 4. CONCLUSIONS AND/OR RECOMMENDATIONS

Through this research, it was possible to develop a product that contributes to a more circular society based on the sustainability tripod. In the social sphere, this research proposed an alternative that allows access to a greater number of women affected by the lack of these essential resources for their lives, promoting greater equality among all. In the economic sphere, this research proposed the use of products that are discarded by industries, providing the appreciation of the circular economy, in addition to promoting cleaner production in industries through the full use of manufactured products; with this, the cost of the product decreases and can also be seen as an alternative to those conventionally used. Finally, in terms of the environment, this research encourages the rational use of resources already used by industries, prioritizing the full use of inputs. With this, it is possible to promote a lower environmental impact by providing a new look at the production of raw materials that use a large amount of water, favoring conscious use throughout the production chain.

The results obtained so far have been promising. It has been possible to obtain, through vegetable fibers, absorbent materials to replace conventional cotton. Also, through the residues of cocoa and the nutraceutical industry, biofilms were obtained to replace the plastic layer. The wrapper that surrounds the two layers mentioned above was made from fabric scraps. The cost of the product was R\$ 0.02, being 95% more economically advantageous than when compared to conventional products, being more accessible to women in situations of vulnerability. All these processes, in addition to providing a more sustainable product, avoid the waste of water present in conventional production processes of commercial tampons and sanitary pads.

Therefore, the present research is important to the environmental, social, economic, and scientific relevance since it provides an alternative to tampons and sanitary pads made from cotton. Also, the alternative is capable of reducing the pollution of water resources due to incorrect disposal of non-biodegradable absorbents and the materials discarded by industries. Thus, the research contributes to the Circular Economy. In addition, the project meets five of the 17 Sustainable Development Goals created by the UN (United Nations), which consist of ensuring health and well-being (number 3) - 3.8: "Achieve universal health coverage, including financial risk protection, access to quality essential health-care services and access to safe, effective, quality and affordable essential medicines and vaccines for all"; gender equality (number 5) - 5.6 "Ensure universal access to sexual and reproductive health and reproductive rights [...]";

sustainable management of water and sanitation (number 6) - 6.2 “By 2030, achieve access to adequate and equitable sanitation and hygiene for all and end open defecation, paying special attention to the needs of women and girls and those in vulnerable situations”; reducing inequalities (number 10) - 10.3 “Ensure equal opportunity and reduce inequalities of outcome [...]” and ensuring consumption and production responsible (number 12) - 12.2 “By 2030, achieve the sustainable management and efficient use of natural resources”; 12.5 “By 2030, substantially reduce waste generation through prevention, reduction, recycling and reuse”; 12.7 “Promote public procurement practices that are sustainable, in accordance with national policies and priorities.

As next steps, analyzes of the functionality of the absorbent prototype and a technological extension will be carried out to bring the product to the community. The technological extension aims to unite the project with what has been happening in the city of Osório, where the city hall is carrying out an action to fight against Period Poverty through a fundraising campaign and donation of hygienic materials. The proposal of a women's cooperative was then conceived so that it is possible to replicate the production of ecological and low-cost sanitary pads, thus providing the generation of income, jobs, and, above all, their belonging within the community.

## 5. REFERENCES

ABDELA, Semira. *Characterization and Efficiency Test of Affordable and Ecofriendly Sanitary Pad Made of Natural Fibers from Enset*. Tese para obtenção do grau de Mestre em Engenharia Biomédica (Instrumentação Biomédica & Imagem). Addis Ababa University School of Graduate Studies - Dez. 2020. Acesso em: 07 jun. 2021

AMERICAN SOCIETY FOR TESTING AND MATERIALS, 2012. **Standard test method for tensile properties of thin plastic sheeting** (D882-12). In: Annual Book of ASTM Standards. American Society for Testing and Materials, Philadelphia, PA. Acesso em: 18 jul. 2021.

ASSOCIATION OF OFFICIAL ANALYTICAL CHEMISTS. **Official methods of analysis of the AOAC**. Washington DC: Association of Official Analytical Chemists, 2005. Acesso em: 18 jul. 2021.

BOROWSKI, Ann. *Are American women turning to reusable and greener menstrual products due to health and environmental pollution concerns?* 80 f. Dissertação (Mestrado) - Civil Engineering Technology Environmental Management and Safety (CAST) of Rochester Institute of Technology, 2011. Acesso em: 10 jun. 2021.

BUSSEY, Cathy. *“Fluffy vagina blankets”*: How Reusable Sanitary Pads Became a Period Phenomenon. Disponível em: <<https://www.telegraph.co.uk/women/womens-life/11871874/Period-product-Sanitary-pads-you-can-reuse.html>>. Acesso em: 28 de dezembro de 2020.

FERREIRA, F.; MACHADO MORAIS, M.; ADEMAR LISSNER, L. *Quantificação de lignina da casca de arroz pelo método Klason*. Anais do Salão Internacional de Ensino, Pesquisa e Extensão, v. 10, n. 2, 3 mar. 2020. Acesso em: 15 out. 2021.

FILHO, José Daladiê Barreto Costa. *Valorização de sabugo de milho: potencial para produção de etanol de segunda geração e uso de lignina residual da hidrólise enzimática como adsorvente de corante catiônico*. Dissertação (mestrado) - Universidade Federal do Rio Grande do Norte, Centro de Tecnologia, Programa de Pós-Graduação em Engenharia Química, Natal, RN, 2021. Acesso em: 15 out. 2021.

GEYER, Roland; JAMBECK, Jenna R.; LAW, Kara Lavender. Production, use, and fate of all plastics ever made. **Science Advances**. 19 jul. 2017. Vol. 3, no. 7. Disponível em: <<https://advances.sciencemag.org/content/3/7/e1700782>>. Acesso em: 02 abr. 2021.

GLOBO RURAL. Algodão brasileiro consome menos água, mas uso de agrotóxicos preocupa, indica relatório. Revista Globo Rural. Disponível em:

<<https://revistagloborural.globo.com/Noticias/Agricultura/Algodao/noticia/2021/04/algodao-brasileiro-consome-menos-agua-mas-uso-de-agrotoxicos-preocupa-indica-relatorio.html>>. Acesso em: 20 de janeiro de 2022.

GOLI, Srinivas et al. *Geographical disparity and socio-demographic correlates of menstrual absorbent use in India: A cross-sectional study of girls aged 15–24 years*. Children and Youth Services Review, v. 117, e105283, ISSN 0190-7409, out. 2020. Acesso em: 09 jul. 2021.

HENRIQUES, André Coelho Vaz. *Empreendedorismo e Consultoria de Recursos Humanos*. [recurso eletrônico]. Porto Alegre: Profissional, 2014. Acesso em: 22 fev. 2022.

IAHNKE, Aline Oliveira e Silva. *Filmes biodegradáveis com propriedades funcionais produzidos a partir de resíduos industriais*. Dissertação para obtenção do grau de Mestre em Ciência e Tecnologia de Alimentos – Universidade Federal do Rio Grande do Sul (UFRGS). Porto Alegre - RS, 2015. Disponível em: <<https://lume.ufrgs.br/handle/10183/129775>>. Acesso em: 14 jun. 2021.

KENAWY, El-Refaie et al. *Superabsorbent composites based on rice husk for agricultural applications: Swelling behavior, biodegradability in soil and drought alleviation*. Journal of Saudi Chemical Society. 2021. Disponível em: <<https://doi.org/10.1016/j.jscs.2021.101254>>. Acesso em: 27 jul. 2021.

MALI, S.; GROSSMANN, M. V. E. & YAMASHITA, F. *Filmes de amido: produção, propriedades e potencial de utilização*-Semina: Ciências Agrárias, Londrina, v. 31, n. 1, p. 137-156, jan./mar. 2010. Acesso em: 02 jun. 2021.

MENDES, Judas Tadeu Grassi. **Economia: Fundamentos e Aplicações**. 2a ed. 309 p. Acesso em: 22 jul. 2021.

MONTGOMERY, D. **Design and Analysis of Experiments**. 7th Edition. New York: John Wiley and Sons, 2008. 680 p. Acesso em: 13 jul. 2020.

NETO, B. B.; SCARMINIO, I. S.; BRUNS, R. E. *Como fazer experimentos: pesquisa e desenvolvimento na ciência e na indústria*. 2 ed. Campinas: Editora Unicamp, 2001. ISBN 85-268-0544-4. Acesso em: 12 set. 2021.

ONU - Organização das Nações Unidas. *Objetivos de Desenvolvimento Sustentável (ODS)*, 2021. Disponível em: <<https://odsbrasil.gov.br/>>. Acesso em: 26 set. 2021.

QUIRINO, Magnólia Grangeiro; SANTOS, Patrícia dos Anjos Braga Sá dos; VASCONCELLOS, Laurino Gomes de Moraes Neto. Compósito laminar produzido com

- a fibra da semente do açaí (Euterpe precatoria). In: ANAIS DO CONGRESSO INTERNACIONAL E WORKSHOP DESIGN & MATERIAIS, 2017, . **Anais eletrônicos...** Campinas, Galoá, 2017. Disponível em: <<https://proceedings.science/dm/papers/composito-laminar-produzido-com-a-fibra-da-semente-do-acai--euterpe-precatoria-->>. Acesso em: 15 ago. 2021.
- PMSN - PRODUCT MANUAL FOR SANITARY NAPKINS ACCORDING TO IS 5405:1980. Sanitary napkins – specification. PM/ IS 5405/1 Sept 2020. Acesso em: 20 jul. 2021.
- SANTOS, Ricardo F. *Empreendedorismo é mais do que abrir uma empresa*. s.d. Disponível em: <<http://revistapegn.globo.com/Revista/Common/0,,EMI141876-17177,00EMPREENDEDORISMO+E+MAIS+DO+QUE+ABRIR+UMA+EMPRESA.html>>. Acesso em: 22 fev. 2022.
- SARAIVA, B. R. et al. 2018. *Valorização de resíduos agroindustriais: fontes de nutrientes e compostos bioativos para a alimentação humana*. Pubsáude, 1, a009. DOI: <https://dx.doi.org/10.31533/pubsaudef1.a007>. Acesso em: 20 mai. 2021.
- SILVA, Everton Menezes da. *Produção e caracterização de filmes biodegradáveis de amido e pinhão*. UFRGS. DEQUI. Trabalho de diplomação em Engenharia Química. Porto Alegre - RS, 2011. Acesso em: 26 fev 2021.
- STEWART, K.; POWELL, M.; GREER, R. *An alternative to conventional sanitary protection: would women use a menstrual cup?*. Journal of Obstetrics and Gynaecology, v. 29, n. 1, p. 49-52, 2009. Acesso em: 13 jan. 2021.
- STOLL, Liana. *Desenvolvimento e aplicação de filmes biodegradáveis com antioxidantes extraídos a partir de bagaço de uva, um resíduo da indústria vitivinícola*. 2015. Dissertação para obtenção do grau de Mestre em Ciência e Tecnologia de Alimentos – Universidade Federal do Rio Grande do Sul (UFRGS). Porto Alegre - RS, 2015. Disponível em:<<https://www.lume.ufrgs.br/handle/10183/129770>>. Acesso em: 02 mai. 2021.
- VASCONCELOS, Yuri. *Planeta Plástico*. Revista Pesquisa FAPESP. Edição 281- jul. 2019. Disponível em: <<https://revistapesquisa.fapesp.br/2019/07/08/planeta-plastico/>>. Acesso em: 03 abr. 2021.
- VIANA, Gustavo. Entenda o que é upcycling e como marcas usam a técnica para criar peças únicas. Folha de São Paulo. Disponível em: <<https://www1.folha.uol.com.br/fsp/fac-simile/2021/09/19/>>. Acesso em: 21 set. 2021.

## **ANNEX A. QUESTIONS ABOUT THE PROJECT**

### **1. What are the major contributions expected with the implementation of this project in view of society, the economy, the environment and especially, water resources?**

The first contribution of this project is to the Period Poverty issue. To meet this demand from society, the product costs only R\$ 0.02, being 95% cheaper than disposable tampons and sanitary pads. Furthermore, with the use of industrial by-products, it contributes to a nobler destination of these residues, avoiding their exacerbated disposal and consequent environmental wear. Hence, the developed solution presents itself as a promising alternative to current synthetic tampons and sanitary pads, which have a large part of their material from non-renewable sources and a high consumption of water in production processes. These products can still end up in oceans and beaches, harming the ecosystem present there. It is in this matter that we highlight the great differential of our proposal: we have developed a product that, in addition to being accessible to consumers (a basic and essential right), is ecological and contributes to the concept of Circular Economy.

### **2. What is the innovation being proposed? How does it relate to existing solutions?**

The importance of this product is related to providing greater accessibility to sanitary pads and at the same time contributing to the environmental issue. Disposable tampons and sanitary pads that are on the market today have a huge environmental impact due to their plastic components and chemical additives. The cotton itself is an expensive and polluting product, given the high use of water and use of pesticides in its plantation. In this way, the research uses materials that would previously be discarded, thus contributing to a better destination of these residues. Currently, there are ecological alternatives, but these are not affordable. This situation makes clear the fact that ecologically correct menstruation is still a luxury for thousands of women who do not even have access to basic hygiene materials. Therefore, the innovative potential lies in the democratization of access to ecologically correct menstruation through a sustainable product that uses industrial waste.

### **3. For which region or situation does the project apply? Can it be replicated? Does it serve developing and developed countries?**

To make our product truly opportunistic for women and to make our contribution to the fight against Menstrual Poverty, we have idealized its application in our community through the creation of a women's cooperative, to democratize the access to this knowledge that we have developed and provide the generation of jobs, sustainable entrepreneurship, and their belonging within the community. We believe that this application is possible since our absorbent has replicability, as we have carried out analyzes with tests in duplicate or triplicate since July 1, 2021, going to the laboratory every day. More than 100 tests were carried out until we reached our best results, which were replicated through factorial planning. The production process is relatively simple, carried out until now on a laboratory scale, and we believe that it will be easier when scaled to an organization such as a cooperative.

#### **4. What is the cost of implementing the project?**

An enterprise has an important role, as it stimulates economic development, job creation and wealth production, and is an important source of innovation in societies (HENRIQUES, 2014). According to Enio Pinto:

*"Entrepreneurship is anything that generates wealth for a society, but you decide what wealth is. It could be employment, quality of life, GDP growth, or getting kids off the streets."* (SANTOS, s.d.).

Observing such concepts, coupled with the fact that Laura takes the Technical Course in Administration Integrated to the EM and learned this in class, the idea of creating an enterprise came up: a cooperative for women to produce sanitary pads. The cost of implementing the project, regarding the constitution of the physical infrastructure of the cooperative, is approximately R\$ 5,000.00. We will also need a minimum of 20 people for the development.

#### **5. What would be or were the biggest difficulties for the development and implementation of the project?**

At the beginning of the project's development, it was very difficult to find the correct process for extracting vegetable fibers, mainly because our school did not have the equipment for this, such as a press. In view of this, we improvised the process using the weight of a car, passed with it over the materials for pressing and subsequent extraction of the fibers. Although it was a great difficulty at the beginning, it was a learning process, reinforcing the importance of persistence and teamwork. Our biggest

challenge today is to implement our product through a women's cooperative in our community. To this end, we have already contacted the city hall of our city, where the first lady has shown full support for the initiative.

**6. Which Sustainable Development Goal (SDG) and targets does your work most relate to?**

The project contributes to five of the 17 Sustainable Development Goals (SDGs) created by the UN (United Nations). They are (UN, n.d):

- N°3: “Ensure healthy lives and promote well-being for all, at all ages.
- N°5 “Achieve gender equality and empower all women and girls”
- N°6: “Ensuring the availability and sustainable management of water and sanitation for all”
- N° 10: “Reducing inequality within and among countries”
- N°12: “Ensure sustainable consumption and production patterns.”.

**What moved you to choose this theme?**

It all started when, in conversation, Camily discovered that her mother didn't have access to tampons and sanitary pads when she was younger. This was the first time that Camily was faced with the issue of Poverty. It was then that she questioned whether it would be possible to have a sanitary pad that, in addition to being ecological, was accessible to women in vulnerable situations. She saw, through science, the opportunity to seek a solution to this problem. So, she invited Professor Flávia to be the advisor. At that moment, Laura joined the team, considering that it was already developing a project on the elaboration of biofilms using industrial waste in 2020. In this way, Laura could contribute with some knowledge (about the production of biofilms) and if unite to provide a solution to such a recurring and serious problem that plagues thousands of women in our society.